

DEKRA Automobil GmbH
Laboratory for Technical Textiles and Films
Breitwiesenstr. 13
70565 Stuttgart
Tel. +49.711.7861-4110
Fax +49.711.7861-4115

Contact:
Jochen Köhnlein
Tel. direct +49.711.7861-4112
E-Mail jochen.koehnlein@dekra.com
Date 15.10.2018

Report on Biaxial Test and Young's Modulus determination

Client:

Sattler PRO-TEX GmbH

Sattlerstraße 45

A-8077 Gössendorf

Index

1. Task	3
2. Introduction	4
3. Theory	6
4. Practical Calculations	8
5. Measuring, Definition of load regime, Calculation of Moduli	9

1. Task

The following biaxial tests has been executed in the lab of DEKRA Technical Textiles and Films according to the client's test requirements and according to DIN EN 17117.

This test was done to determine the Young's Modulus.


Testing temperature:	23 °C ± 2 K
Date of receipt:	25.09.2018
Date of test:	26.09.2018
Supplier of sample:	Sattler PRO-TEX GmbH, Gössendorf, Austria
Material manufacturer:	Sattler PRO-TEX GmbH, Gössendorf, Austria
Material type:	PVC coated Polyester fibre fabric
Material application type:	739 ATLAS Architecture Type II
Batch no:	
Production no.:	
Internal sample no.:	M18/1430
Load regime:	611-14 Art 739 LG E-Modul
Load conditions:	warp to weft stresses 1:1, 2:1, 1:2, 1:0, 0:1 pre stress 1.1 kN/m

2. Introduction

There are different methods to determine the elastic moduli of a coated fabric.


First we have to mention that we want to establish a linear elastic approximation for a non-linear non-elastic behaviour. Furthermore we assume that a fabric behaves as an orthotropic two dimensional material. And we want to simulate only the behaviour under stresses the mean axes of which are parallel to warp and weft.

In the following picture 2.1 a normal load regime to determine the elastic moduli is shown.

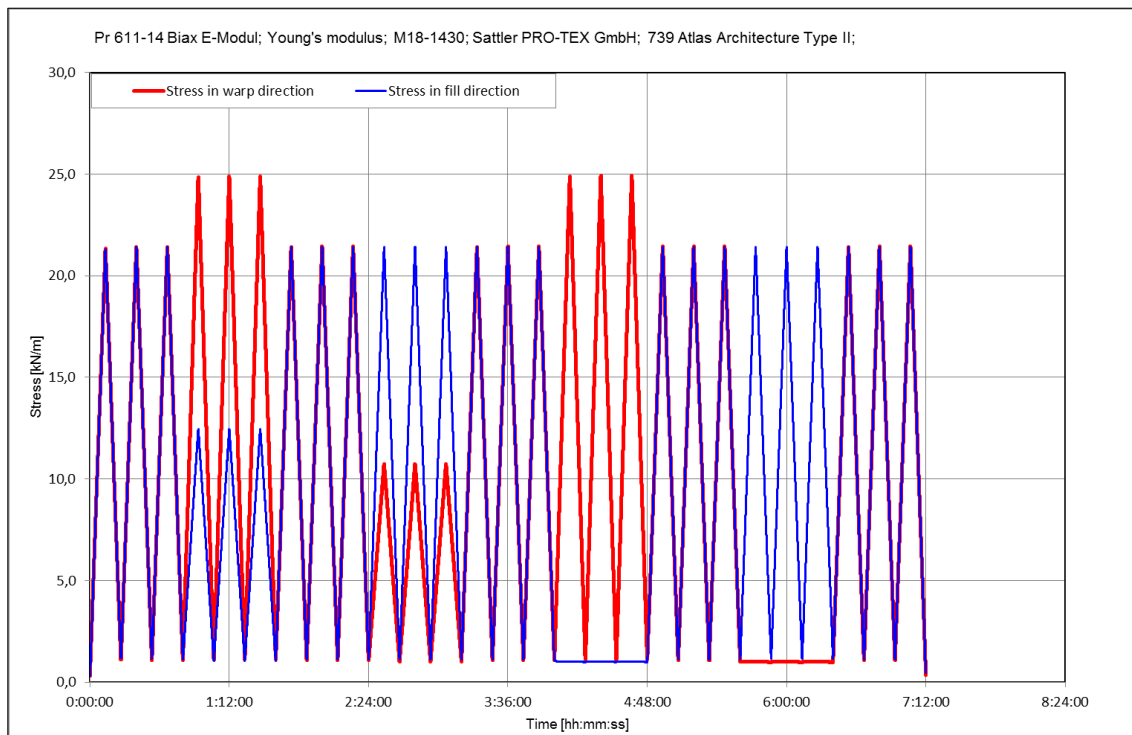

Picture 2.1: Load regime for the determination of the elastic moduli

In the second picture we will show a usual diagram for the stress-strain-relations. In many cases the moduli are now calculated as the gradient of a tangent in a chosen working point, normally the prestress which is sketched here.

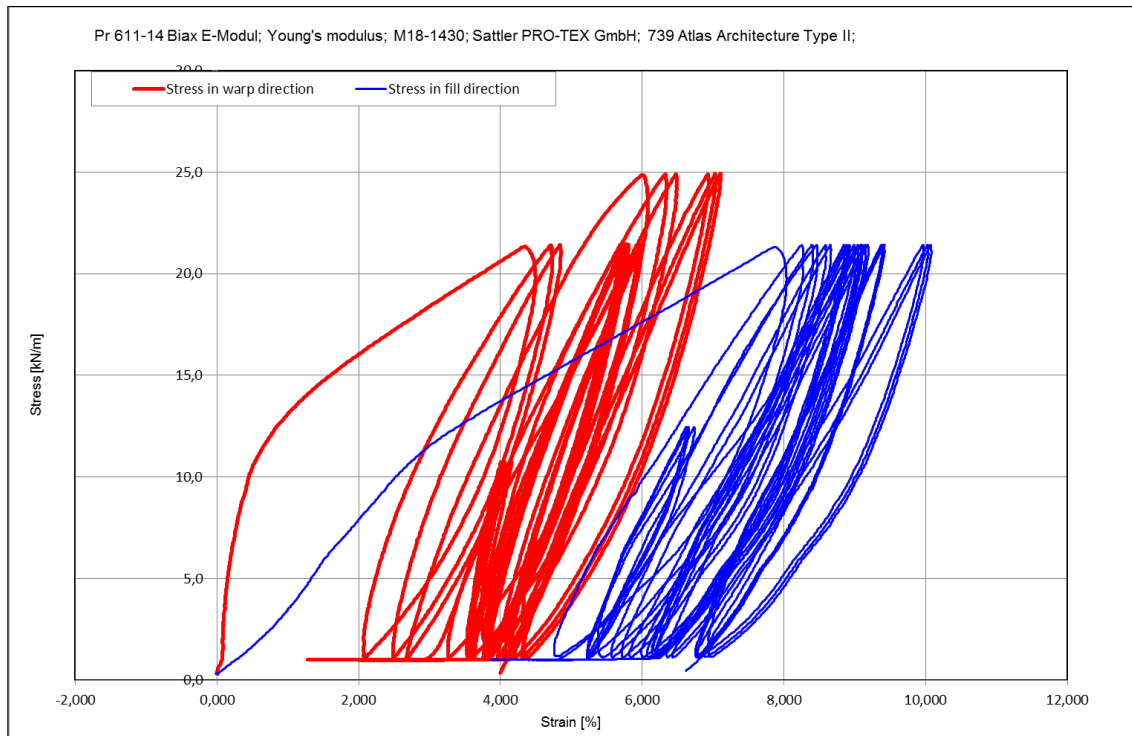

Picture 2.2: Stress strain diagram

We will show that this procedure can be critical in some cases and that we propose another procedure.

3. Theory

In linear elastic approximation for orthotropic behaviour we have the following relations:

$$\begin{bmatrix} n_{11} \\ n_{22} \end{bmatrix} = \begin{bmatrix} E_{1111} & E_{1122} \\ E_{1122} & E_{2222} \end{bmatrix} \begin{bmatrix} \varepsilon_{11} \\ \varepsilon_{22} \end{bmatrix}$$

with the inversion:

$$\begin{bmatrix} \varepsilon_{11} \\ \varepsilon_{22} \end{bmatrix} = \begin{bmatrix} C_{1111} & C_{1122} \\ C_{1122} & C_{2222} \end{bmatrix} \begin{bmatrix} n_{11} \\ n_{22} \end{bmatrix}$$

or, explicitly:

$$n_{11} = E_{1111} \varepsilon_{11} + E_{1122} \varepsilon_{22} = E_{1111} (\varepsilon_{11} + \nu_{12} \varepsilon_{22})$$

$$n_{22} = E_{1122} \varepsilon_{11} + E_{2222} \varepsilon_{22} = E_{2222} (\nu_{21} \varepsilon_{11} + \varepsilon_{22})$$

with the inversion:

$$\varepsilon_{11} = C_{1111} n_{11} + C_{1122} n_{22}$$

$$\varepsilon_{22} = C_{1122} n_{11} + C_{2222} n_{22}.$$

Index 11 is used for warp direction, index 22 for fill (weft) direction. For stresses n is used, ε for strains, E is used for Young's modulus in the respective direction and C is used for compliance.

The following abbreviations are used:

n_{11} stress in warp direction,

n_{22} stress in fill direction

ε_{11} strain in warp direction,

ε_{22} strain in fill direction

E_{1111} stiffness in warp direction,

E_{2222} stiffness in fill direction,

E_{1122} stiffness interaction between warp and fill,

$\nu_{12} = E_{1122}/E_{1111}$ Poisson ratio for the interaction between warp and fill

$\nu_{21} = E_{1122}/E_{2222}$ Poisson ratio for the interaction between fill and warp

C_{1111} compliance in warp direction,

C_{2222} compliance in fill direction,

C_{1122} compliance interaction between warp and fill.

We have used four indices both for stiffness and compliance to manifest that these terms are tensors of fourth order which link two tensors of second order, the stresses \mathbf{n} and the deformations $\mathbf{\epsilon}$ linearly. With this statement the behaviour under transformation is well defined.

4. Practical Calculations

When the slopes of each load cycle is taken, using the equation:

$$\begin{bmatrix} \Delta\varepsilon_{11} \\ \Delta\varepsilon_{22} \end{bmatrix} = \begin{bmatrix} C_{1111} & C_{1122} \\ C_{1122} & C_{2222} \end{bmatrix} \begin{bmatrix} \Delta n_{11} \\ \Delta n_{22} \end{bmatrix}$$

the following two equations are obtained:

$$\Delta\varepsilon_{11} = C_{1111} \cdot \Delta n_{11} + C_{1122} \cdot \Delta n_{22}$$

and


$$\Delta\varepsilon_{22} = C_{1122} \cdot \Delta n_{11} + C_{2222} \cdot \Delta n_{22}.$$

The elastic modulus is then:

$$\bar{E} = \frac{1}{\det C} \begin{bmatrix} C_{2222} - C_{1122} \\ -C_{1122} C_{1111} \end{bmatrix}.$$


5. Measuring, Definition of load regime, Calculation of Moduli

Now we have applied the load regime shown above in picture 2.1. The resulting strains are shown in picture 5.1.

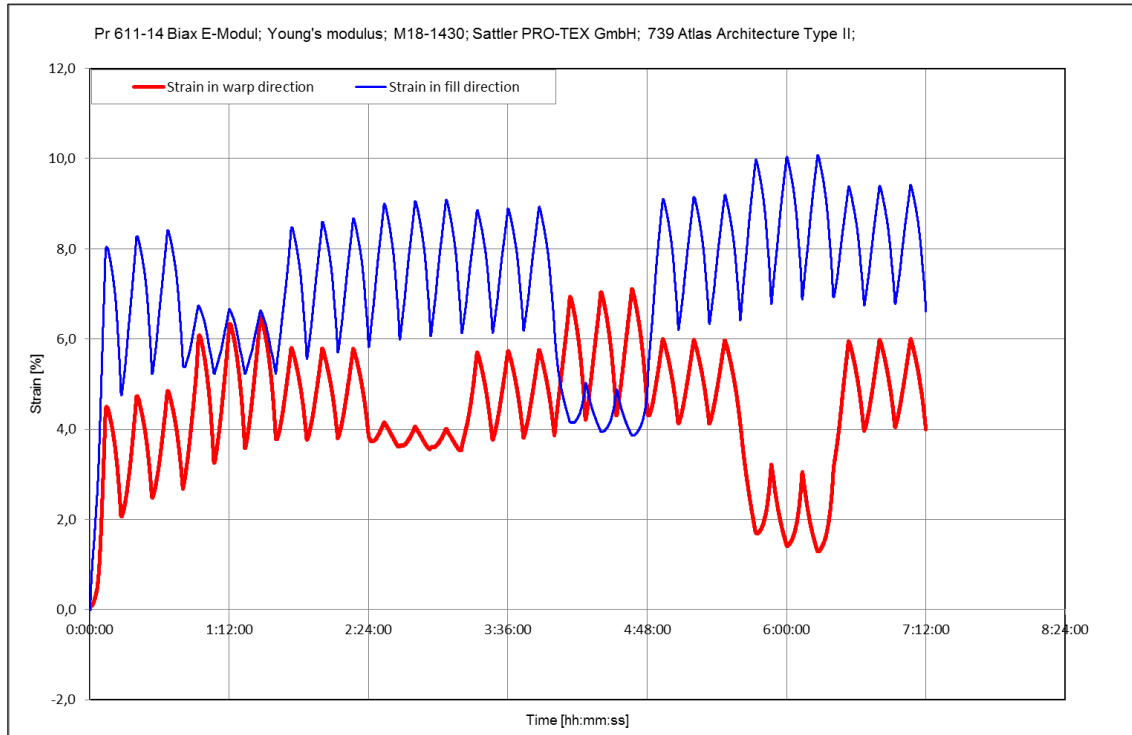

Picture 5.1: Resulting Strains

In Picture 5.2 the evaluation of the results is shown for example.

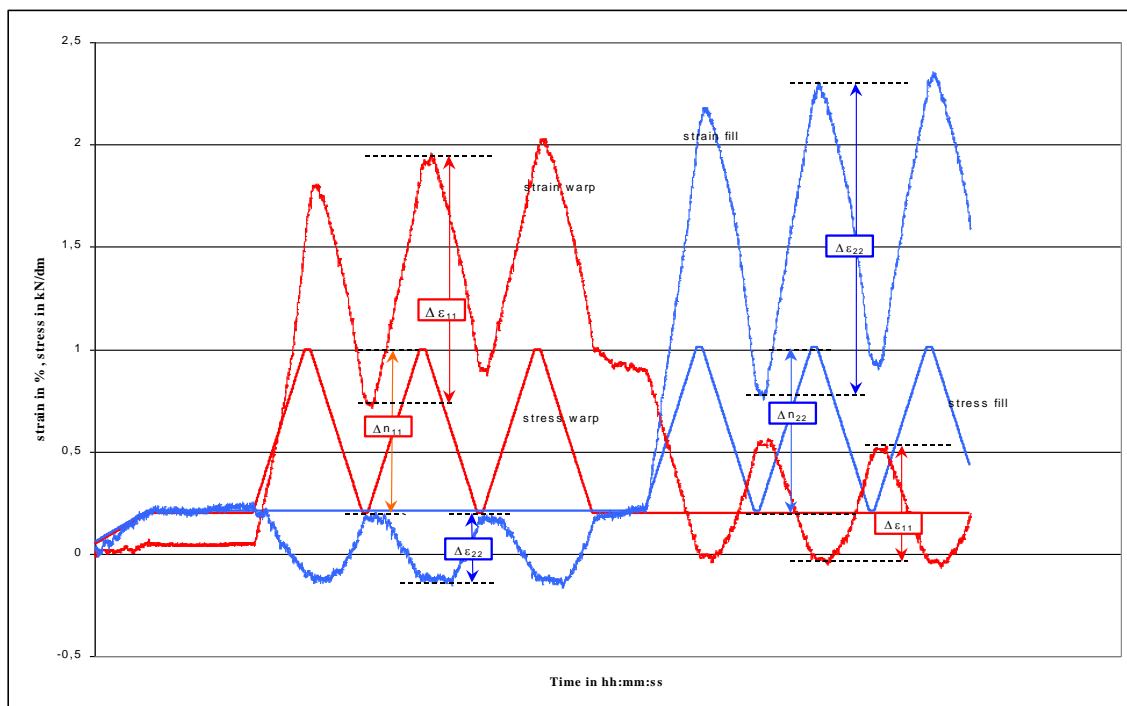

Picture 5.2: Evaluation of elastic moduli

Evaluating is made with the strain results as shown in picture 5.1. The differences of stress values and of strain values will be taken for each relationship of ratio (Δn_{11} , $\Delta \varepsilon_{11}$, Δn_{22} , $\Delta \varepsilon_{22}$...) The results are written down in table 5.1. Then calculation will be done for relation of stress combination as shown in the following table 5.2.

The classical formulation of stress – strain in table 5.2 are taking into account the Poisson's ration, they will be often used in appropriate known calculation programs (finite elements analysis).

For comparison, the evaluations of the individual cycles are also listed, where it should be shown that these are not to be regarded as representative.

Table 5.1: Differences of stress and strain and average values for different stress ratio

warp to weft stress ratio	last 2 cycles				averages			
	Δn_{11}	Δn_{22}	$\Delta \varepsilon_{11}$	$\Delta \varepsilon_{22}$	Δn_{11}	Δn_{22}	$\Delta \varepsilon_{11}$	$\Delta \varepsilon_{22}$
	kN/dm *min	kN/dm *min	%/min	%/min	kN/dm *min	kN/dm *min	%/min	%/min
1:1	0,256	0,256	0,270	0,400	0,256	0,256	0,266	0,395
	0,256	0,256	0,262	0,390				
2:1	0,300	0,144	0,402	0,190	0,300	0,144	0,396	0,188
	0,300	0,144	0,390	0,186				
1:2	0,122	0,256	0,058	0,401	0,122	0,256	0,058	0,399
	0,122	0,256	0,058	0,396				
1:0	0,300	0,000	0,366	-0,138	0,300	0,000	0,366	-0,134
	0,300	0,000	0,366	-0,129				
0:1	0,000	0,256	-0,226	0,422	0,000	0,256	-0,224	0,419
	0,000	0,256	-0,222	0,415				

Table 5.2: Elastic moduli in dependency of stress ratio combination

		warp to weft stress ratio combination						
		1:1 2:1	1:1 1:2	1:1 1:0	1:1 0:1	2:1 1:0	1:2 0:1	all combi- nations
E_{1111}	kN/m	661	647	848	536	791	452	698
E_{1122}	kN/m	143	111	133	159	40	144	170
E_{2222}	kN/m	593	641	520	628	432	636	609
ν_{12}		0,22	0,17	0,16	0,30	0,05	0,32	0,24
ν_{21}		0,24	0,17	0,26	0,25	0,09	0,23	0,28
<i>classical evaluation</i>								
$E_{1111} \cdot \text{resp. } E_{2222} \cdot (1 - E_{1122}^2 / (E_{1111} \cdot E_{2222}))$ respectively								
$\varepsilon_{11} = \sigma_{11} / E_1 - \nu_{12} \cdot \sigma_{22} / E_2$; $\varepsilon_{22} = \sigma_{22} / E_2 - \nu_{21} \cdot \sigma_{11} / E_1$ mit $E_1 \cdot \nu_{12} = E_2 \cdot \nu_{21}$								
E_1	kN/m	627	628	814	496	787	419	
E_2	kN/m	562	622	499	581	430	590	
<i>evaluation from single sloping graph</i>								
		1:1	2:1	1:2	1:0	0:1		
E_1	kN/m	962	758	2103	820	0		
E_2	kN/m	648	766	642	0	612		

Young's modulus determination is valid only for the calculated loads.

The results of the biaxial test above should not be used for compensation.

Remark:

All test results are only referring to the above-mentioned samples. A publication in extracts is only allowed in accordance with DEKRA (Automobil GmbH) Laboratory for Technical Textiles and Films.

Stuttgart, 15.10.2018



Dipl.-Ing. Jochen Köhnlein
Technical manager



Prof. Dr.-Ing. Heidrun Bögner-Balz
Laboratory manager